arXiv:1408.4058v1 [cond-mat.supr-con] 18 Aug 2014

Structural origin of the anomalous temperature dependence of the local magnetic moments in the $CaFe_2As_2$ family of materials

L. Ortenzi,[1,2] H. Gretarsson,[2,3] S. Kasahara,[4] Y. Matsuda,[4] T. Shibauchi,[5,4] K. D. Finkelstein,[6] W. Wu,[3] S. R. Julian,[3] Young-June Kim,[3] I. I. Mazin,[7] and L. Boeri[8]

[1]*Institute for Complex Systems (ISC), CNR, U.O.S. Sapienza, v. dei Taurini 19, 00185 Rome, Italy*
[2]*Max-Planck-Institut für Festkörperforschung, Heisenbergstraβe 1, D-70569 Stuttgart, Germany*
[3]*Department of Physics, University of Toronto, 60 St. George St., Toronto, Ontario, M5S 1A7, Canada*
[4]*Department of Physics, Kyoto University, Kyoto 606-8502, Japan*
[5]*Department of Advanced Materials Science, The University of Tokyo, Japan*
[6]*Cornell High Energy Synchrotron Source, Cornell University, Ithaca, New York 14853, USA*
[7]*code 6390, Naval Research Laboratory, 4555 Overlook Avenue SW, Washington, DC 20375, USA*
[8]*Institute for Theoretical and Computational Physics, TU Graz, Petersgasse 16, 8010 Graz, Austria.*

(Dated: August 19, 2014)

We report a combination of Fe Kβ x-ray emission spectroscopy and *ab*-intio calculations to investigate the correlation between structural and magnetic degrees of freedom in $CaFe_2(As_{1-x}P_x)_2$. The puzzling temperature behavior of the local moment found in rare earth-doped $CaFe_2As_2$ [*H. Gretarsson, et al., Phys. Rev. Lett.* **110**, *047003 (2013)*] is also observed in $CaFe_2(As_{1-x}P_x)_2$. We explain this phenomenon based on first-principles calculations with scaled magnetic interaction. One scaling parameter is sufficient to describe quantitatively the magnetic moments in both $CaFe_2(As_{1-x}P_x)_2$ ($x = 0.055$) and $Ca_{0.78}La_{0.22}Fe_2As_2$ at all temperatures. The anomalous growth of the local moments with increasing temperature can be understood from the observed large thermal expansion of the *c*-axis lattice parameter combined with strong magnetoelastic coupling. These effects originate from the strong tendency to form As-As dimers across the Ca layer in the $CaFe_2As_2$ family of materials. Our results emphasize the dual local-itinerant character of magnetism in Fe pnictides.

It is generally believed that superconductivity in Fe-based materials (FeBS) is related to magnetic fluctuations. [1, 2] However, from the very beginning two schools were formed as regarding the best description of magnetism in these systems. One described the Fe moments as soft and itinerant and related magnetic interactions to the Fermi surface properties. [3–5] The other assumed localized moments not unlike those in cuprates that interact via superexchange-type interactions. [6, 7] At a later stage it was proposed that the truth is in-between, namely that the moments are substantially localized, and large, but they are nonetheless soft (can easily change their amplitude, not just direction), strongly coupled to the lattice (the amplitude strongly depends on the pnictogen's position), formed by itinerant electrons, and are greatly reduced by fluctuations. [8–12]

$CaFe_2As_2$ and its derivatives are an odd case among the Fe-based superconductors (FeBSs). Under pressure the parent compound collapses into a new structure, with a much shorter *c*-axis lattice parameter and smaller As-As distance. [13] The crystal structure of $CaFe_2As_2$ at an ambient pressure, like that of all other FeBSs, is very well described by the density functional theory (DFT) calculations, *if the moments are allowed to grow to their DFT values,* which can be more than a factor of two larger than the measured *ordered* moments. In those FeBSs in which long-range order is suppressed by means other than pressure, the crystal structure is still predicted correctly by the magnetic DFT, and not by its nonmagnetic variant. This strongly suggests that sizeable local moments are present also in FeBSs which do not show long-range magnetic order.

Conversely, the high-pressure collapsed tetragonal (cT) structure of $CaFe_2As_2$ is accurately described by *non-magnetic* DFT calculations, in agreement with the fact that the local moments are quenched in this phase. [14] This magnetic collapse in $CaFe_2As_2$ has a structural origin, namely the reduced As-As distance across the Ca layer, and is now fully understood on the basis of DFT calculations. [15–18] Experiments also find that the magnetic moments in $CaFe_2As_2$ are very sensitive to this As-As distance. [19, 20]

Besides pressure, structural and magnetic transitions can be modulated through rare-earth [21] or phosphorous [22] substitutions. In this work we will show that in these compounds not only the ordered moments, but also the local moments are exceptionally soft, and their counterintuitive growth with increasing temperature is due to the negative chemical pressure exerted upon Fe by the lattice expansion.

Some of us had shown before that the shape of the Fe Kβ emission line in x-ray emission spectroscopy (XES) can be used to measure the local moment in FeBSs. [23, 24] In this paper, we employ this technique to study the temperature dependence of the magnetic moment in $CaFe_2(As_{1-x}P_x)_2$ ($x = 0$, $x = 0.033$ and $x = 0.055$), combined with high-quality X-Ray diffraction data, and show that the anomalous increase of the magnetic moment with temperature correlates with a strong *c*-axis expansion. DFT calculations as a

function of the lattice parameter, including an effective fluctuation-induced renormalization of the magnetic moment, [25, 26] quantitatively reproduce the increase of the local moment in this compound, as well as in the previously measured $Ca_{0.78}La_{0.22}Fe_2As_2$. [24] This unambiguously demonstrates that the observed effect is not related to thermal *excitations* but to thermal *expansion*, combined with the unique softness of the Fe moments in $CaFe_2As_2$.

The XES measurements were performed at the Cornell High-Energy Synchrotron Source (CHESS) on the bending magnet beamline C1. Incident energy of 9 keV (1% bandwidth) was selected from a multilayer monochrometer. To measure the Fe Kβ emission line, we used five Ge(620) 4" spherical analyzers (1 m radius) and a Vortex detector in quasi-Rowland circle geometry. X-ray diffraction measurements were performed using a Cu tube source with a Ge(111) monochromator. Samples were aligned within a four-circle Huber diffractometer. The temperature dependence of the *c*-axis was determined by monitoring the (008) Bragg peak. Data was collected on cooling using a closed-cycle refrigerator. Details of the growth of the single-crystal samples have been reported before. [27]

The ground state of $CaFe_2(As_{1-x}P_x)_2$ has been shown to be very sensitive to small inhomogeneity in doping and crystal growth conditions; [22, 28] we thus carefully characterized all our samples using x-ray diffraction. In Fig. 1 (a) the thermal evolution of the *c*-axis lattice constant in $CaFe_2(As_{1-x}P_x)_2$ can be seen. Both the parent compound and the $x = 0.033$ sample exhibit a first-order tetragonal(T)- to orthorhomic(O)-phase transition (T_O) around 165 K and 130 K, respectively. Upon increasing x further, T_O gets suppressed and eventually superconductivity appears for $x \sim 0.04$. [22] At $x = 0.055$ superconductivity disappears and a sharp transition into the collapsed-tetragonal(cT) phase is seen at 80 K (T_{cT}). For comparison we also include data on $Ca_{0.78}La_{0.22}Fe_2As_2$ from Ref. 24. This compound stays in the T-phase over the entire temperature range and thus provides "a bridge" between the $x = 0.033$ and $x = 0.055$ samples.

Fig. 1 (a) already reveals the unique feature of $CaFe_2As_2$ materials, an enormous lattice constant change with temperature. Even for the samples that do not exhibit the cT-phase transition (e.g. $x = 0.033$), the c-axis contraction ($\sim 100\times10^{-5}$ Å/K) in the T-phase is already three times larger than what we have observed in the related compound $BaFe_2As_2$ ($\sim 35\times10^{-5}$ Å/K). [29] Interestingly, this rate of contraction is not seen in the magnetically ordered O-phase, emphasizing the important role of magnetism in these materials.

In order to investigate if this large change in the *c*-axis lattice parameter is coupled to the magnetic moment of Fe, we carried out Fe Kβ ($3p \rightarrow 1s$) XES experiment. By applying the integrated absolute difference (IAD) analysis [30] on the shape of the emission line information

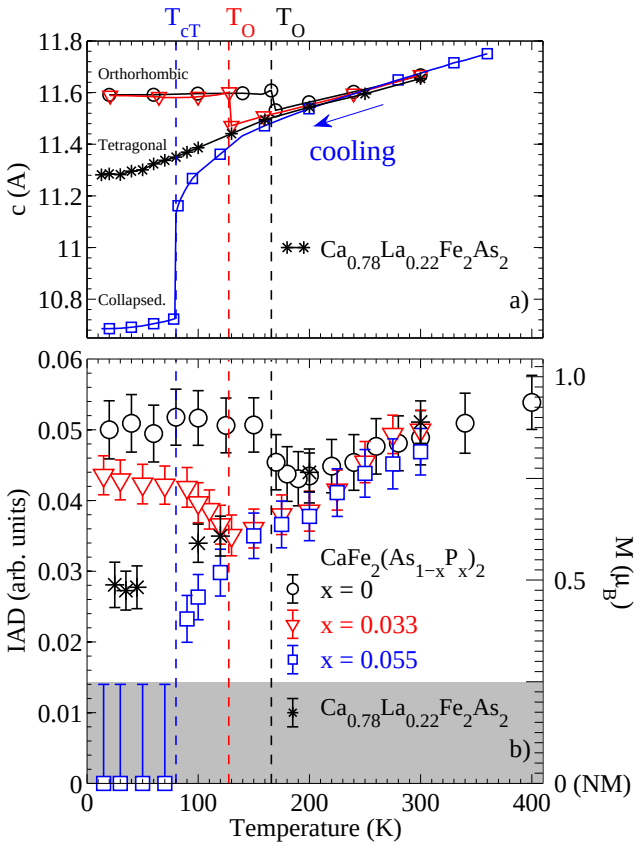

FIG. 1: (Color online) (a) Temperature dependence of the *c*-axis lattice parameter in $CaFe_2(As_{1-x}P_x)_2$. Both $x = 0$ and $x = 0.033$ samples go through tetragonal- to orthorhomic-phase transition (T_O) around 165 K and 130 K, respectively. In the $x = 0.055$ an abrupt transition into collapsed-tetragonal phase is seen at 80 K (T_{cT}). (b) The temperature dependence of the IAD values for the same samples derived from their XES spectra. On the right-hand side is the magnetic moment of Fe (M) derived as described in text. Data for $Ca_{0.78}La_{0.22}Fe_2As_2$ – Ref. 24 – are also shown for comparison.

on the size of the Fe magnetic moment can be obtained (see Supplemental Material for details). As in our previous work, [23, 24] the reference spectra for low-spin and high-spin were FeCrAs and $K_2Fe_4Se_5$, respectively. In Fig. 1 (b) the temperature dependence of the IAD values for all samples can be seen. Since the IAD is found to be linearly proportional to the magnetic moment of Fe (M) [31] we can add to the plot a right-hand axis showing the local moment scale, as determined from the IAD values of FeCrAs and $K_2Fe_4Se_5$. The detection limit of the IAD technique is shown as a shaded area. [24] By comparing our results on $CaFe_2(As_{1-x}P_x)_2$ with the one obtained for $Ca_{0.78}La_{0.22}Fe_2As_2$ we notice a similar temperature behavior of the local moment. At room temperature all samples have local moments around 0.8 μ_B, which upon cooling gradually decreases. The $x = 0.055$ sample shows the strongest effect, going from ≈ 0.8 μ_B

at $T = 300$ K, to 0.4 μ_B at 100 K, and in the cT-phase it drops to zero. A similar trend can be seen in the T-phase for both the parent compound and $x = 0.033$, although to a lesser extent. Interestingly, in their magnetically ordered O-phase an increase in the moment is observed which gradually becomes temperature independent upon further cooling.

Our observation in Fig. 1 highlights the similarities between the evolution of the c-axis lattice parameter and the measured magnetic moment for both $CaFe_2(As_{1-x}P_x)_2$ and $Ca_{0.78}La_{0.22}Fe_2As_2$. In particular, both M and c strongly depend on temperature in the T-phase, but not in the antiferromagnetic O-phase, demonstrating a strong entanglement between the structural and magnetic degrees of freedom.

The unusual thermal sensitivity of the c-axis lattice parameter in $CaFe_2As_2$ and its derivatives, combined with the well-known sensitivity of the magnetic moments in Fe pnictides to the Fe-As and As-As distances [32, 33], hints at the importance of the lattice geometry and thermal expansion. In order to investigate a possible *structural* origin of the anomalous behavior of the magnetic moment, we performed first-principles calculations of the magnetic moment as a function of the experimental, temperature-dependent lattice parameters for both La-doped and P-doped ($x = 0.055$) samples from Refs. 21, 22. [34, 36, 38]

In order to correct the well-known tendency of standard local (spin) density approximation - L(S)DA - and generalized gradient approximation (GGA) exchange and correlation (xc) functionals to overestimate the size of the magnetic moment in Fe pnictides, we used the Reduced Stoner Theory (RST) introduced by some of us in Ref. 26. In practice, we introduced a scaling parameter $0 < s < 1$ for the spin-dependent part of the exchange and correlation functional, which accounts for the reduction of the magnetic moment due to spin fluctuations, in the spirit of Moriya's self-consistent theory. [25] The value of s in a given material indicates the importance of spin fluctuations: $s = 1$ reproduces the standard exchange and correlation functional (i.e. no additional fluctuation effects are included), while for $s = 0$ fluctuations are so strong that magnetism is entirely suppressed. [26] Importantly, while the original Moriya's theory only deals with the ordered moment, by integrating over all fluctuations with all frequencies, one expects the same approach, but with reduced renormalization (smaller $1 - s$) to work also for the local moments. Obviously, the scaling parameter in this case should depend on the time scale of the experiment probing the local moments; since in our experiment the time scale is independent of doping and temperature, we should be able, if this theory is correct, to explain the experiment using the same s for all samples and temperatures.

With this in mind, we have fixed s so as to reproduce the magnetic moment at the highest temperature (T = 300 K) for the La-doped sample, and found that without changing s the full temperature dependence of the magnetic moment for all measured samples could be reproduced.

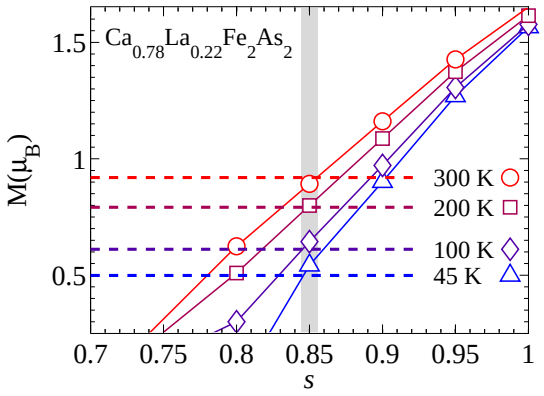

FIG. 2: (Color online) Magnetic moment M of $Ca_{0.78}La_{0.22}Fe_2As_2$ as a function of the DFT-RST scaling parameter s for different temperatures (solid lines). The horizontal dashed lines show the experimental values of the magnetic moment for different temperatures taken from Ref. 24. Best agreement with experimental values is obtained using $s = 0.85$ (gray vertical line).

In Fig. 2 we show the scaling effect for $Ca_{0.78}La_{0.22}Fe_2As_2$. For $s = 1$, corresponding to standard LSDA calculations, the magnetic moment is almost temperature-independent, but for smaller s the moment acquires a stronger T-dependence, until magnetism is entirely suppressed below $s \approx 0.75$. The value of $s = 0.85$ reproduces experimental data at all temperatures nearly perfectly. This is even more clearly seen in Fig. 3 (a), where the magnetic moments for $s = 0.85$ and $s = 1$ are plotted as a function of temperature.

Fig. 3 (b) shows the same calculations for the P-doped samples at $x = 0.055$ (blue squares in Fig. 1 (b)). Experimentally, this sample turns into a non-magnetic collapsed tetragonal phase below $T_{cT} = 80$ K; the complete set of structural parameters and internal coordinate of the As is published in Ref. 22. As can be seen in Fig. 3 (b), the standard DFT overestimates M and underestimates its temperature dependence, although it correctly converges to a nonmagnetic ground state in the cT-phase ($T = 10$ K). The same $s = 0.85$ as used for the La-doped compound reproduces remarkably well the experimental behavior. [39] Interestingly, we had not been able to describe with a single s the behavior of the ordered moment near the doping-induced quantum critical point (QCP) in $BaFe_2As_2$. [40] This is understandable, because (i) a QCP generates much stronger fluctuations than a first-order structural collapse and (ii) more fluctuations contribute to renormalization of the ordered moment than to the local one.

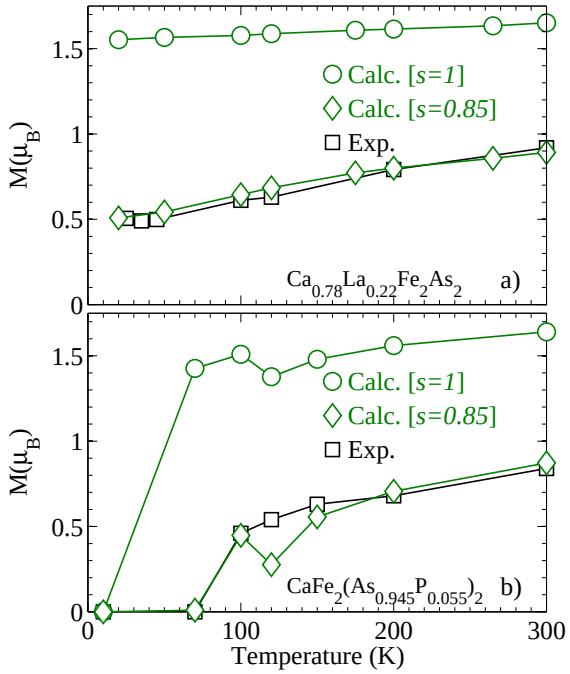

FIG. 3: (Color online) Magnetic moment as a function of temperature in the DFT-RST calculations using $s = 0.85$ (diamonds) compared with the experimental data (squares) of (a) $Ca_{0.78}La_{0.22}Fe_2As_2$ (Ref. 24) and (b) $CaFe_2As_{0.945}P_{0.055}$. The hollow circles indicate conventional LSDA results (equivalent to DFT-RST with $s = 1.00$).

In DFT, the origin of the magnetic collapse of the 122 structure is a subtle balance between the energy gain induced by lattice collapse, discussed in a seminal paper by Hoffmann and Zheng, [18] and the magnetic energy gained in the uncollapsed phase. The magnetic stabilization energy in Fe pnictides is discussed in detail in Ref. 41, using a simplified non-self-consistent version of reduced Stoner theory. This quantity depends in a non-trivial way on the value of the magnetic moment and on the details of the electronic structure, and a discussion is beyond the scope of the present paper. Two observations are however in place: (a) an anti-ferromagnetic (AFM) ground state can be stabilized only if d_{xy} electronic states are present at the Fermi level in the non-magnetic DFT band structure; [17] (b) the transition from the uncollapsed to the collapsed tetragonal phase results in a relative shift of the d_{xy} states with respect to other d states, but the change in occupation is so small ($\Delta n_{xy} \simeq 0.1$ e/unit cell) that it does not make sense to talk of a spin-state transition.

A pronounced temperature-dependence of a magnetic moment is often associated with some thermal excitations. With this in mind, the experimental data on $Ca_{0.78}La_{0.22}Fe_2As_2$, were fitted in Ref. 24 with a model assuming thermally excited low-high spin transitions, similar to the strongly correlated insulator $LaCoO_3$ [42]. This model implies narrow Fe d levels that could form two nearly degenerate magnetic states, whose relative occupation changes with temperature. An essential part of this model is an assumption that some or all electrons form localized narrow states, separated by a crystal field comparable with the Hund's rule coupling, so that localized electrons on a site can form two nearly degenerate states, a singlet and a triplet. An alternative version of the same model instead of using temperature to mix these two states utilizes an empirical magnetoelastic coupling. A proper tuning of the model ensured a good description of the experimental data. [24, 43] However, the fundamental assumption of this model does not seem to be applicable to $CaFe_2As_2$. First, as opposed to $LaCoO_3$, in $CaFe_2As_2$ the bandwidths for all orbitals are large, and, most importantly, all the crystal field splittings are much smaller than either the Hund's rule coupling J or the bandwidths. Thus, in actuality the materials appear to be in a completely different regime, where the softness of the magnetic moment is derived not from an accidental degeneracy of two ionic states (*i.e.*, from a competition between the Hund's rule and crystal field) but from the competition between the Hund's rule and kinetic energy. Our approach is aimed at capturing exactly this competition. The fact that only with one parameter we were able to describe two different, albeit similar material, testifies that this is the correct physics.

In conclusion, in this work we have addressed the issue of the intriguing and counterintuitive growth of local magnetic moments with temperature in the $CaFe_2As_2$ family of materials. We have shown that this phenomenon is present not only in the La-doped system, [24] but also in $CaFe_2(As_{1-x}P_x)_2$, suggesting that it is universal for all Ca-based 122 materials, and ruling out explanations requiring fine parameter tuning. Using density functional theory, we found that in both materials, again counterintuitively, the observed strong temperature dependence is not related to any thermally excited process, but is a consequence of the anomalously large thermal expansion along c, combined with strong magnetoelastic coupling, both due to As-As interaction across the (relatively thin) Ca layer. Therefore cooling the sample is equivalent to applying pressure on it. This finding emphasizes the dual character of magnetism in the parent materials of Fe-based superconductors, where sizable local moments are nonetheless soft and exhibit many traits of itinerant magnetism.

The authors acknowledge useful discussions with G. Khaliullin. IIM acknowledge support from ONR through NRL basic research program, and from the A.v. Humboldt foundation. Research at the University of Toronto was supported by the NSERC, CFI, OMRI, and CIfAR. Use of the Cornell High Energy Synchrotron Source (CHESS) was supported by the National Science Foundation and the National Institutes of Health/National Institute of General Medical Sciences under NSF award DMR-

0936384. LO acknowledge support from the Deutsche Forschungsgemeinschaft under Priority Program 1458, grant number Boe/3536-1.

[1] P.J. Hirschfeld, M.M. Korshunov, I.I. Mazin Reports on Progress in Physics **74**, 124508 (2011).

[2] A. Chubukov, Ann. Rev. of Cond. Matt. Phys, **3**, 57 (2012).

[3] I.I. Mazin, D.J. Singh, M.D. Johannes, and M.H. Du, Phys. Rev. Lett. **101**, 057003 (2008).

[4] A. V. Chubukov, D. V. Efremov, and I. Eremin Phys. Rev. B **78**, 134512 (2008).

[5] Fa Wang, Hui Zhai, and Dung-Hai Lee, Europhys. Lett. **85**, 37005 (2009).

[6] Qimiao Si, Elihu Abrahams, Phys. Rev. Lett. **101**, 076401 (2008).

[7] Kangjun Seo, A. B. Bernevig and JiangPing Hu Phys. Rev. Lett **101**, 206404 (2008).

[8] I.I. Mazin and M.D. Johannes Nature Physics **5**, 141 (2009).

[9] I.I. Mazin and M.D. Johannes Phys. Rev. B **79**, 220510 (R) (2009).

[10] S.J. Moon, J.H. Shin, D. Parker, W.S. Choi, I.I. Mazin, Y.S. Lee, J.Y. Kim, N.H. Sung, B.K. Cho, S.H. Khim, J.S. Kim, K.H. Kim, and T.W Noh, B **81**, 205114 (2010).

[11] Z. P. Yin, K. Haule, and G. Kotliar, Nat. Mat. **10**, 932 (2011).

[12] P. Hansmann, R. Arita, A. Toschi, S. Sakai, G. Sangiovanni, and K. Held Phys. Rev. Lett. **104**, 197002 (2010).

[13] A. Kreyssig, M. A. Green, Y. Lee, G. D. Samolyuk, P. Zajdel, J. W. Lynn, S. L. Bud'ko, M. S. Torikachvili, N. Ni, S. Nandi, J. B. Leão,S. J. Poulton, D. N. Argyriou, B. N. Harmon, R. J. McQueeney, P. C. Canfield, and A. I. Goldman Phys. Rev. B **78** 184517 (2009).

[14] Pratt, D. K et al. Phys. Rev. B **79**, 060510(R) (2009).

[15] T. Yildirim, Phys. Rev. Lett. **102**, 037003 (2009).

[16] A. Sanna, G. Profeta, S. Massidda, and E. K. U. Gross, Phys. Rev. B **86**, 014507 (2012).

[17] R. S. Dhaka, R. Jiang, S. Ran, S. L. Bud'ko, P. C. Canfield,M. Tomič and R. Valentí, Y. Lee, B. N. Harmon and A. Kaminski, Phys. Rev. B **89**, 02511(R) (2014).

[18] R. Hoffmann and C. Zheng J. Phys. Chem., **89** (20), 4175 (1985).

[19] J. R. Jeffries, N. P. Butch, M. J. Lipp, J. A. Bradley, K. Kirshenbaum, S.R. Saha, J. Paglione, C. Kenney-Benson, Y. Xiao, P. Chow, and W. J. Evans, arXiv 1401.7400 (2014).

[20] J. H. Soh, G. S. Tucker, D. K. Pratt, D. L. Abernathy, M. B. Stone, S. Ran, S. L. Bud'ko, P. C. Canfield, A. Kreyssig, R. J. McQueeney, A. I. Goldman Phys. Rev. Lett. **111**, 227002 (2013).

[21] S. R. Saha, N. P. Butch, T. Drye, J. Magill, S. Ziemak, K. Kirshenbaum, P. Y. Zavalij, J. W. Lynn, and J. Paglione Phys. Rev. B **85** 024525 (2012).

[22] S. Kasahara, T. Shibauchi, K. Hashimoto, Y. Nakai, H. Ikeda, T. Terashima, and Y. Matsuda Phys. Rev. B **83** 060505(R) (2011).

[23] H. Gretarsson, A. Lupascu, Jungho Kim, D. Casa, T. Gog, W. Wu, S. R. Julian, Z. J. Xu, J. S. Wen, G. D. Gu, R. H. Yuan, Z. G. Chen, N.-L. Wang, S. Khim, K. H. Kim, M. Ishikado, I. Jarrige, S. Shamoto, J.-H. Chu, I. R. Fisher, and Young-June Kim Phys. Rev. B **84**, 100509(R) (2011).

[24] H. Gretarsson, S. R. Saha, T. Drye, J. Paglione, Jungho Kim, D. Casa, T. Gog, W. Wu, S. R. Julian, and Young-June Kim, Phys. Rev. Lett. **110**, 047003 (2013).

[25] T. Moriya, Spin Fluctuations in Itinerant Electron Magnetism, Springer Series in Solid-State Science (1985).

[26] L. Ortenzi, I. I. Mazin, P. Blaha, and L. Boeri, Phys. Rev. B **86**, 064437 (2012).

[27] Kasahara, S. and Shibauchi, T. and Hashimoto, K. and Ikada, K. and Tonegawa, S. and Okazaki, R. and Shishido, H. and Ikeda, H. and Takeya, H. and Hirata, K. and Terashima, T. and Matsuda, Y., Phys. Rev. B 81 184519 (2010).

[28] Ran, S. *et al.*, Phys. Rev. B **83**, 144517 (2011).

[29] H. Gretarsson et al., *unpublished*.

[30] G. Vanko *et al.*, J. Phys. Chem. B **110**, 11647 (2006).

[31] G. Vanko, J. P. Rueff, A. Mattila, Z. Nemeth and A. Shukla, Phys. Rev. B **73**, 024424 (2006).

[32] Yin, Z. P. and Lebegue, S. and Han, M. J. and Neal, B. P. and Savrasov, S. Y. and Pickett, W. E., Phys.Rev. Lett. **101**, 047001 (2008).

[33] Mazin, I. I. and Johannes, M. D. and Boeri, L. and Koepernik, K. and Singh, D. J., Phys.Rev. B **78**, 085104 (2008).

[34] http://www.wien2k.at.

[35] J.P. Perdew and Y. Wang, Phys.Rev. B **45**, 13244 (1992).

[36] All calculations were performed with the full-LAPW code Wien2K [34], using a LSDA exchange and correlation functional. [35] Up to 3374 **k** points in the irreducible wedge were used in the self-consistent calculations, corresponding to a $30 \times 30 \times 27$ mesh.

[37] J. P. Perdew, K. Burke, and M. Ernzerhof, Phys. Rev. Lett. **78**, 1396 (1997).

[38] For the La-doped compound the position of the As atoms was determined at each temperature with a DFT optimization, based on the standard PBE exchange and correlation functional, [37] and not the fluctuation-corrected DFT described below.

[39] One may note some disagreement at $T = 120$ K; however, the error bar on this particular point is large, since the experimental data for the internal As coordinates at this temperature have a large uncertainity. In fact, for this (and only this) point the optimized As coordinate differs substantially from the reported experimental one.

[40] L. Ortenzi, I. I. Mazin, and L. Boeri, *unpublished*.

[41] O.K. Andersen, L. Boeri Ann. Phys. **1**, 8-50 (2011).

[42] T. Saitoh *et al.*, Phys. Rev. B **55**, 4257 (1997).

[43] J. Chaloupka and G. Khaliullin, Phys. Rev. Lett. **110** 207205 (2013).

arXiv:1408.4058v1 [cond-mat.supr-con] 18 Aug 2014

Supplemental Material: Structural origin of the anomalous temperature dependence of the local magnetic moments in the $CaFe_2As_2$ family of materials

L. Ortenzi,[1,2] H. Gretarsson,[2,3] S. Kasahara,[4] Y. Matsuda,[4] T. Shibauchi,[5,4] K. D. Finkelstein,[6] W. Wu,[3] S. R. Julian,[3] Young-June Kim,[3] I. I. Mazin,[7] and L. Boeri[8]

[1]*Institute for Complex Systems (ISC), CNR, U.O.S. Sapienza, v. dei Taurini 19, 00185 Rome, Italy*
[2]*Max-Planck-Institut für Festkörperforschung, Heisenbergstraβe 1, D-70569 Stuttgart, Germany*
[3]*Department of Physics, University of Toronto, 60 St. George St., Toronto, Ontario, M5S 1A7, Canada*
[4]*Department of Physics, Kyoto University, Kyoto 606-8502, Japan*
[5]*Department of Advanced Materials Science, The University of Tokyo, Japan*
[6]*Cornell High Energy Synchrotron Source, Cornell University, Ithaca, New York 14853, USA*
[7]*code 6390, Naval Research Laboratory, 4555 Overlook Avenue SW, Washington, DC 20375, USA*
[8]*Institute for Theoretical and Computational Physics, TU Graz, Petersgasse 16, 8010 Graz, Austria.*

(Dated: August 19, 2014)

S1. Fe Kβ emission line and the size of the local moment

The local moment sensitivity of the Fe Kβ emission line ($3p \rightarrow 1s$) originates from a large overlap between the $3p$ and $3d$ orbitals. This interaction is mainly driven by the presence of a net magnetic moment (μ) in the $3d$ valence shell [S1, S2] and causes the Kβ emission line to split into a main peak K$\beta_{1,3}$ and a low-energy satellite Kβ'. A schematic diagram of the Fe Kβ emission process is shown in Fig. S1 inset for both non-magnetic (red) and magnetic (blue) Fe^{2+} in the atomic limit. Filled and empty circles represent electrons and holes, respectively, and ΔE represents the splitting of K$\beta_{1,3}$ and Kβ'. Information on the local moment of Fe can be extracted using the overall shape of the Fe Kβ emission spectra by applying the integrated absolute difference (IAD) analysis. [S3]

In Fig. S1 we show the Fe Kβ emission line of $CaFe_2(As_{1-x}P_x)_2$ ($x = 0.055$) taken at T = 300 K along with a non-magnetic FeCrAs reference spectrum. [S4, S5, S6] Relative to the main line in FeCrAs, we see that the K$\beta_{1,3}$ peak of the $x = 0.055$ sample shifts towards higher energy while the intensity and the width of this peak also change; a contribution from Kβ' on the lower energy side becomes visible now. These changes are all attributed to the existence of a local moment. To follow the IAD procedure from Ref. S3, the area underneath each spectrum was normalized to unity. The reference spectrum was then subtracted from the sample spectrum, and the resulting difference plotted. For display purpose, the difference was magnified by a factor of 4. The IAD value can be extracted by integrating the absolute value of the difference spectrum. This quantity is found to be linearly proportional to the local spin magnetic moment of the Fe atom. [S7]

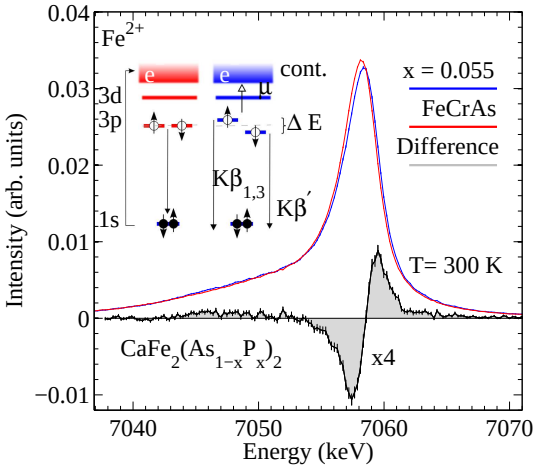

FIG. S1: (Color online) Comparison of the Fe Kβ emission line ($3p \rightarrow 1s$) of $CaFe_2(As_{1-x}P_x)_2$ ($x = 0.055$) and FeCrAs taken at T = 300 K. Each spectrum was normalized to unity and the difference plotted (gray). The difference spectra was magnified by a factor of 4. The inset shows the Kβ emission process in the atomic limit (see text).

S2. Temperature dependence of the Fe Kβ emission line

Fe Kβ emission lines obtained at different temperatures are shown in Fig. S2 (a) - (d) for both $x = 0.055$ and $x = 0.033$ samples. At T = 300 K the $x = 0.033$ sample shows the same characteristics as the $x = 0.055$. However, at T = 15 K significant changes can be observed, the K$\beta_{1,3}$ in the $x = 0.055$ sample shifts towards lower energy and the contribution from Kβ' is suppressed. This is well captured in the difference spectra, which shows a complete suppression and provides evidence for a quenched local moment. The $x = 0.033$ sample show opposite trend, from T = 130 K to T = 15 K the difference spectra grows modestly indicating that the local moment increases as the sample enters the

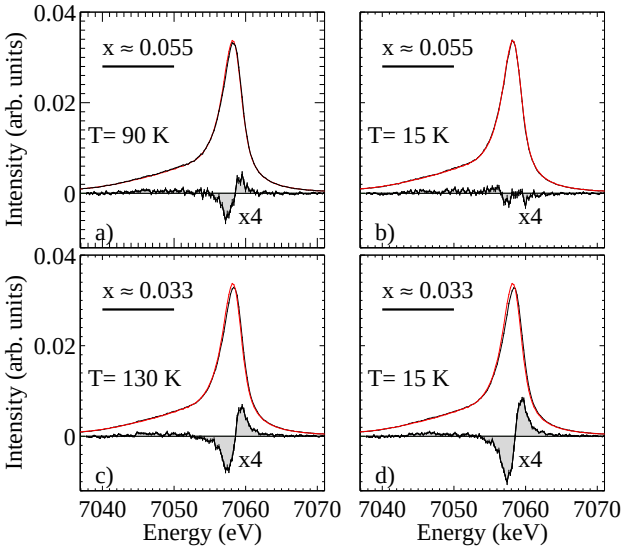

FIG. S2: (Color online) Comparison of the Fe Kβ emission line ($3p \rightarrow 1s$) of $CaFe_2(As_{1-x}P_x)_2$ (black line) and FeCrAs (red line) for $x = 0.055$ at (a) T = 90 K and (b) T = 15 K, and for $x = 0.033$ at (c) T = 130 K and (d) T = 15 K. Each spectrum was normalized to unity and the difference plotted (gray). The difference spectra was magnified by a factor of 4.

magnetically ordered tetragonal phase.

[S1] K. Tsutsumi *et al.*, Phys. Rev. B **13**, 929 (1976).
[S2] G. Peng *et al.*, J. Am. Chem. Soc. **116**, 2914 (1994).
[S3] G. Vanko *et al.*, J. Phys. Chem. B **110**, 11647 (2006).
[S4] H. Gretarsson, *et al.*, Phys. Rev. B **84**, 100509(R) (2011).
[S5] W. Wu *et al.*, Europhys. Lett. **85**, 17009 (2009).
[S6] S. Ishida *et al.*, Physica B **217**, 87 (1996).
[S7] G. Vanko *et al.*, Phys. Rev. B **73**, 024424 (2006).